

pca

european journal of
postclassicalarchaeologies

volume 6/2016

SAP Società Archeologica s.r.l.

Mantova 2016



EDITORS

Gian Pietro Brogiolo (chief editor)

Alexandra Chavarría (executive editor)

ADVISORY BOARD

Martin Carver (University of York)

Matthew H. Johnson (Northwestern University of Chicago)

Giuliano Volpe (Università degli Studi di Foggia)

Marco Valenti (Università degli Studi di Siena)

ASSISTANT EDITOR

Francesca Benetti

LANGUAGE EDITOR

Rebecca Devlin (University of Florida)

EDITORIAL BOARD

Gilberto Artioli (Università degli Studi di Padova)

Andrea Breda (Soprintendenza BB.AA. della Lombardia)

Margarita Diaz-Andreu (ICREA - Universitat de Barcelona)

José M. Martín Civantos (Universidad de Granada)

Girolamo Fiorentino (Università del Salento)

Caterina Giostra (Università Cattolica del Sacro Cuore di Milano)

Susanne Hakenbeck (University of Cambridge)

Vasco La Salvia (Università degli Studi G. D'Annunzio di Chieti e Pescara)

Bastien Lefebvre (Université Toulouse - Jean Jaurès)

Alberto León (Universidad de Córdoba)

Tamara Lewit (Trinity College - University of Melbourne)

Federico Marazzi (Università degli Studi Suor Orsola Benincasa di Napoli)

Dieter Quast (Römisch-Germanisches Zentralmuseum Mainz)

Andrew Reynolds (University College London)

Mauro Rottoli (Laboratorio di archeobiologia dei Musei Civici di Como)

Colin Rynne (University College Cork)

Post-Classical Archaeologies (PCA) is an independent, international, peer-reviewed journal devoted to the communication of post-classical research. PCA publishes a variety of manuscript types, including original research, discussions and review articles. Topics of interest include all subjects that relate to the science and practice of archaeology, particularly multidisciplinary research which use specialist methodologies, such as zooarchaeology, paleobotany, archaeometallurgy, archaeometry, spatial analysis, as well as other experimental methodologies applied to the archaeology of post-classical Europe.

Submission of a manuscript implies that the work has not been published before, that it is not under consideration for publication elsewhere and that it has been approved by all co-authors. Each author must clear reproduction rights for any photos or illustration, credited to a third party that he wishes to use (including content found on the Internet). For more information about **ethics** (including plagiarism) and copyright practices and guidelines please visit the web site www.postclassical.it.

PCA is published once a year in May, starting in 2011. Manuscripts should be submitted to editor@postclassical.it in accordance to the guidelines for contributors in the webpage <http://www.postclassical.it>

Post-Classical Archaeologies's manuscript **review process** is rigorous and is intended to identify the strengths and weaknesses in each submitted manuscript, to determine which manuscripts are suitable for publication, and to work with the authors to improve their manuscript prior to publication.

This journal has the option to publish in **open access**. For information please visit the web site www.postclassical.it

How to **quote**: please use "PCA" as abbreviation and "Post-Classical Archaeologies" as full title.

Cover image: courtesy of Schaffhausen, Stadtbibliothek (Switzerland), Gen. 8, f. 271v – Klosterneuburger Evangelienwerk, retrieved from www.e-codices.unifr.ch/en/sbs/0008/271v/0/Sequence-1030

"Post-Classical Archaeologies" was approved on 2015-05-13 according to ERIH PLUS criteria for inclusion. Classified A by ANVUR (Agenzia Nazionale di Valutazione del sistema Universitario e della Ricerca).

DESIGN

Paolo Vedovetto

PUBLISHER

SAP Società Archeologica s.r.l.
Strada Fienili 39/a, 46020 Quingentole, Mantova
www.archeologica.it

PRINTED BY

Tecnografica Rossi, Via I maggio, Sandrigo (VI)

Authorised by Mantua court no. 4/2011 of April 8, 2011

For subscription and all other information visit the web site www.postclassical.it

CONTENTS PAGES

EDITORIAL

5

RESEARCH - RECYCLING AND REUSE IN THE MIDDLE AGES

- R. Fleming The ritual recycling of Roman building material in late 4th- and early 5th-century Britain

7

- S. Paynter, C. Jackson Re-used Roman rubbish: a thousand years of recycling glass

31

- A. Sebastiani Glass and metal production at Alberese. The workshops at the manufacturing district of Spolverino

53

- F.-D. Deltenre, L. Orlandi «Rien ne se perd, rien ne se crée, tout se transforme». Transformation and manufacturing in the Late Roman *villa* of Aiano-Torraccia di Chiusi (5th-7th cent. AD)

71

- S. Bertoldi Santa Cristina in Caio (Buonconvento, Si): productive reuse during the Late Antiquity and the Early Middle Ages

91

- C. Fernández-Ochoa, F. Gil Sendino, J. Salido La actividad metalúrgica en el yacimiento Veranes (Gijón, España): de la villa romana al asentamiento tardoantiguo y altomedieval

109

BEYOND THE THEME

- F. Curta Postcards from Maurilia, or the historiography of the dark-age cities of Byzantium

141

- M. Asolati Trasparenze ponderali: contrappesi monetali di vetro nell'Anatolia bizantina

163

DOSSIER - WORLD HERITAGE AND THE PUBLIC

- M. Díaz-Andreu** Introduction to the Dossier "World Heritage and the Public" 189
- M. Díaz-Andreu** Social values and the participation of local communities in World Heritage: a dream too far? 193
- Q. Gao** Social values and archaeological heritage: an ethnographic study of the Daming Palace archaeological site (China) 213
- G. Alexopoulos, K. Fouseki** Gender exclusion and local values versus universal cultural heritage significance: the Avaton debate on the monastic community of Mount Athos 235
- T.S. Guttormsen, J. Taylor, G. Swensen** Heritage values conceptualised as heritage routes. Visions and challenges towards public diversity 255
- M. Maluck** Spatial planning as a way to stakeholder involvement in cultural heritage management. Examples from Northern Europe 273
- D. Rodwell** Community values vs World Heritage values: bridging the gap 295
- G.P. Brogiolo** The UNESCO network "The Longobards in Italy. The Places of Power (568-774 A.D.)" and the Brescia case 317

RETROSPECT

- N.I. Platonova** Problems of early medieval Slavonic Archaeology in Russia (a view from St. Petersburg) 333

PROJECT

- M. Valenti** "We invest in Public Archaeology". The Poggibonsi Archaeodrome project: an alliance between people, Municipality and University 417

REVIEWS

- G. Chouquer**, *Les parcellaires médiévaux en Émilie et en Romagne. Centuriations et trames coaxiales. Morphologie et droit agraires* - by **C. Citter** 431
- A. Vigil-Escalera Guirado**, *Los primeros paisajes altomedievales en el interior de Hispania. Registros campesinos del siglo quinto d.C.* - by **T. Lewit**
- M. Díaz-Andreu, A. Pastor Pérez, A. Ruiz Martínez** (eds), *Arqueología y comunidad. El valor social del Patrimonio Arqueológico en el Siglo XXI* - by **M. del Carmen Rojo Ariza**

EDITORIAL

The sixth issue of PCA presents the material from two conferences held in different European countries last year.

The volume opens with some of the papers presented at The British School at Rome (April 2014) at a conference on The Recycling and Reuse of Materials during the Early Middle Ages. The meeting – organised by Alessandro Sebastiani (who has collaborated as guest editor for this section), Elena Chirico and Matteo Colombini – dealt mainly with productive structures related to the transformation of glass and metal in Italy (papers by Alessandro Sebastiani, Stefano Bertoldi, François-Dominique Deltenre and Lucia Orlandi). Other international experts have agreed to add their contributions to the subject: Robin Fleming on the reuse of construction material in early medieval graves, Sarah Paynter and Caroline Jackson offering a synthesis on the reuse of glass, and the team of Carmen Fernández-Ochoa in Spain presenting the early medieval productive structures at the villa of Veranes (Gijón). Two papers by Florin Curta and Michele Asolati, dealing with exchange in the Byzantine Mediterranean, have been published in the Varia section.

After the catastrophe of World War II, many international institutions were founded: the United Nations, UNESCO, the European Community. All these organizations are today immersed in a transitional phase in the systemic crisis which affects the entire Western world, a crisis to which the nihilist and relativist positions have contributed and which has (rightly) delegitimated the imperialism on which the West had built its dominant position. In this crisis, the recovery of shared historical memories is increasingly revealed as a central element in the defence of a rational world, which, although it may have abandoned the utopias of the 1900s, at least safeguards the principles of freedom and the pluralism of values. Today, there is wide debate, even among archaeologists, over how to present cultural heritage in a globalized society while nevertheless pre-

serving its multiple identities and cultures. The discussion of these matters was the purpose of the papers dedicated to the World Heritage List. This collection, guest edited by Margarita Díaz-Andreu, results from a workshop of the EU-project JPI–JHEP Heritage Values Network (H@V) held at the University of Barcelona in February 2015. The main question, summarized in the title of the paper by Díaz-Andreu, is whether the inclusion of social values and local communities in the management of cultural heritage is an impossible dream. Is it a utopian vision, typical of the historical processes which gave birth to the international organizations and their initiatives to hold back the spectre of a World War III? In many of these contributions, the watchwords still conform to this direction: the participation and involvement of stakeholders in the hope that local communities will be led to a positive valuation of assets and their public use.

The different directions of the debate move between the two poles of economic management and cultural enrichment of local communities. Too often, it is difficult to find a balance between touristic exploitation and a useful cultural proposal for local communities, as happened in the telling example of the Daming Palace in China, developed by Qian Gao, winner of the 2016 PCA young researcher award.

Direct involvement is often difficult in a globalized and multicultural society that has lost its historical roots. Most of the contributions consider that a proper balance can be found between global strategies promoted by UNESCO, based on the decalogue of general principles under which to file an application for protected sites, and the feeling and evaluation expressed by the local community (the focus of Torgrim Sneve Guttorsen, Joel Taylor, Grete Swensen on Heritage Routes and Matthias Maluck and Gian Pietro Brogiolo on organizational proposals in the interventions).

Also related to the subject of cultural heritage and the public is the project section of this issue, a homage the Poggibonsi Archeodromo. A project developed in recent years by the team of Marco Valenti (University of Siena), this is a unique living archaeological park recreated from archaeological evidence, presenting the life of an early medieval village, an initiative that clearly demonstrates the social and economic benefits of good practices in public archaeology in Italy.

Finally, the retrospect section, which addresses the history of early medieval archaeology in different European countries, is this year devoted to the fascinating recent history of early medieval Archaeology in Russia, with an extensive study by Nadezhda Platonova (St Peterburg).

Re-used Roman rubbish: a thousand years of recycling glass

SARAH PAYNTER *
CAROLINE JACKSON **

* Historic England, Fort Cumberland, Fort Cumberland Road, Eastney, Portsmouth PO4 9LD, UK. Corresponding author: sarah.paynter@historiceengland.org.uk
** Department of Archaeology, University of Sheffield, Northgate House, West Street, Sheffield S1 4ET, UK, c.m.jackson@sheffield.ac.uk

The suitability of glass for re-melting and recycling was widely exploited in the past. This paper reviews the evidence, particularly for the 1st millennium AD, using examples from Western Europe. For much of this period glass was produced on a large-scale at a relatively small number of specialised glassmaking sites, which supplied numerous dispersed workshops where glass was modified and shaped. This is only part of the picture however, because the glassmakers, glassworkers and consumers were also linked by a complex, interdependent cycle of supply, use, discard, salvage and re-use, making recycling an essential part of interpreting archaeological glass.

Keywords: glass, recycling, 1st millennium AD, Western Europe

Nel passato la caratteristica del vetro di poter essere rifuso, e dunque riciclato, venne ampiamente sfruttata. L'articolo esamina le evidenze di questa pratica nel primo millennio d.C., utilizzando esempi dell'Europa Occidentale. Per gran parte di questo periodo il vetro fu prodotto su larga scala in un numero relativamente piccolo di siti specializzati, che rifornivano laboratori preposti alla sua lavorazione. Questa è tuttavia solo una parte del quadro, perché i produttori di vetro, gli artigiani e i consumatori erano anche collegati a un complesso ciclo di rifornimento, uso, scarto, recupero e riuso. La comprensione del ciclo è dunque un fattore essenziale nell'interpretazione del vetro in archeologia.

Parole chiave: vetro, riciclo, I millennio d.C., Europa Occidentale

1. Introduction

Glass can be repeatedly re-melted and re-used. This property was exploited by the earliest producers of glass in Egypt and the Near East in the 2nd millennium BC, where glass ingots were made and then traded to be re-melted at sites which produced beads, inlays and vessels, in a variety of colours. In addition to melting newly-made glass, scrap glass could also be recycled. This re-use and recycling of glass was common even in

the earliest glass-using societies and sometimes undertaken on a large scale. By the early Roman period for instance, recycling is documented in texts which hint at the infrastructure and organisation of the trade in broken glass, or 'cullet', across the empire (see Keller 2005, pp. 67-68).

The importance of glass recycling to our understanding of where and how glass was produced, and who used it in the past, is increasingly recognised, especially by those studying glass compositions (Jackson 1996, 2005a; Silvestri *et al.* 2008; Schibille, Freestone 2013; Jackson, Paynter 2015; Freestone 2015). Nevertheless, there is still much to discover about how and why the scale, economic significance, motivation and methods for recycling varied in the past (Grünewald, Hartmann 2015). The act of recycling is an essential and integral part of the *chaîne opératoire* and biography of glass production, which has to be considered in order to fully understand the range of glass forms, colours and compositions found in archaeological material. Unaltered glass compositions, those which have not been mixed through recycling, contain chemical markers that allow us to investigate the origins of the raw materials, and hence the locations, of glass production. When glass is recycled however, these compositions become contaminated and mixed, potentially diminishing our ability to access that inherent archaeological information that allows us to trace the movement of glass from source. Our challenge now is to reveal the repeating and interlocking trails of production, trade, working, use, discard and re-working in recycled glass; this can be done by linking a variety of different forms of evidence.

This paper focuses on the 1st millennium AD, exploring the different ways in which recycling can be detected in the archaeological record. A combination of contextual and scientific analysis, documentary accounts and typological studies are used to illustrate the difficulties faced by archaeologists when interpreting chemical data for glasses, but also how a more nuanced interpretation is often possible when recycling is considered. Our examples have been chosen to represent a wide geographical and chronological spread, from the Roman period through to the 12th century AD, for both transparent and strongly coloured opaque glass.

2. Glass production in the 1st millennium AD

Wide reaching studies, for example by Sayre and Smith (1961), Turner (1956) and Brill (1999), have shown that the raw materials used for glass production, and the sources of those materials, have varied over time. This makes glass special: unlike pottery which could be made with a variety of available materials processed in any number of ways result-

ing in a virtually infinite range of compositions and textures, glass was made with very carefully selected raw materials, which for most of the 1st millennium AD were only obtained from a small number of locations. As a result early glass compositions, before about the 10th century AD in the western world, tend to be relatively homogenous over long periods of time and space. When changes do occur in compositions, they are quite marked and perhaps reflect significant social, economic or political upheavals, affecting trade routes, the social groups controlling production, the production process or the raw materials used.

The common denominator in ancient glass production was a source of silica, which was often sand or alternatively crushed quartz, flint or other siliceous stone. The silica was combined with fluxes and heated to make a molten glass that could be shaped into objects. A variety of fluxes were used in the past, including the ashes of plants, lead compounds or the alkali-rich evaporitic deposit natron. Whilst plant ashes were favoured in the ancient western world prior to the mid-1st millennium BC and again in the 2nd millennium AD, mineral alkalis (natron) tend to dominate the archaeological record in the 1st millennium AD in Europe, Egypt and parts of the Near East (Smith 1963; Uboldi, Verità 2003). Roman accounts of glassmaking describe using natron from the Wadi Natrun in Egypt, which was harvested seasonally from the edges of salt lakes, in combination with sand (Jackson *et al.* in preparation). The glass appears to have been made on a vast scale in large tank furnaces located at sites in the Eastern Mediterranean (Brill 1988; Nenna 2015). In tank furnaces the glass cooled as a massive slab, which was later broken up into large lumps and redistributed to workshops throughout the empire and beyond for shaping into vessels and window panes, or coloured and shaped into beads, bangles or tesserae (Foy *et al.* 2000; Keller 2005; Freestone 2006; Paynter *et al.* 2015).

Freshly made natron glass was transparent but often had a light blue or green tint (known as naturally-coloured blue-green glass) ranging to olive green or brownish tones. The colour was derived from small quantities of iron minerals in the raw materials (fig. 1). Some of this glass was modified by adding manganese or antimony oxides, which could partially or completely neutralise the colour; antimony oxide was a particularly effective decolouriser resulting in high quality colourless glass (Jackson, Paynter 2015). Alternatively the glass could be given a strong colour, and made opaque, by adding metal minerals or compounds, for example copper produced blue, green or red, cobalt a dark blue and manganese (in sufficient quantities) a dark purple (fig. 2). An understanding of the colouring and decolourising of glass is important for our understanding of glass recycling.



Fig. 1. A collection of naturally-coloured cullet from Roman London (courtesy of MOLA).

Establishing the way in which the composition of glass changes over-time, how widely available each glass type was, and what different types were used for, has been an important first step in detecting recycling. This is particularly the case for the 1st millennium AD, because of the unique way glass production and distribution was organised (Freestone 2006; Nenna 2015). It has been shown that the majority of new glass was made in a limited number of locations and so only a relatively small number of natron glass compositions have been identified. Each of these compositions, or 'production groups', has a particular lifespan and exhibits diagnostic chemical characteristics. This 'Roman glass' was consumed widely during the Roman period throughout Western Europe and the regions bordering the Mediterranean sea. Typically some of these glasses were used selectively only for certain objects (Foy *et al.* 2003) so it is easier to identify glass that has been altered, mixed, reused or contaminated (Jackson, Paynter 2015). Even during this period when glass was relatively plentiful, there is evidence of extensive recycling and natron glass continued to be used and recycled into the beginning of the 2nd millennium AD within the region. Subsequently the organisation of production changed dramatically such that glass was made in numerous locations from diverse locally available raw materials (rather than natron), resulting in a vast range of compositions, and it is at this point recycling becomes more difficult to detect.

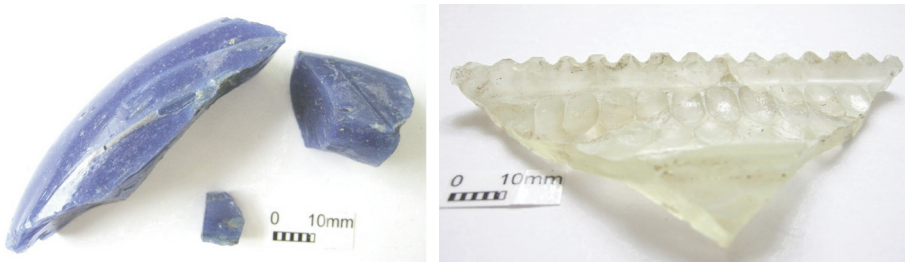


Fig. 2. Roman colourless glass and opaque strongly coloured glass (from Binchester, Durham, and Great Bentley, Essex, respectively) both containing high concentrations of antimony, characteristic of much Roman colourless and coloured glass.

3. Detecting recycling in the past

3.1. Archaeological evidence

The archaeological context and typological examination of an assemblage often provide the first clues that recycling has taken place. Large collections of cullet, sometimes numbering thousands of fragments of broken glass and glass waste collected for recycling, are relatively common finds throughout the period discussed here. Cullet dumps in the Roman world have been found associated with military camps, villas and towns (Keller 2005; Grünewald, Hartmann 2015); a number of large collections of cullet have been found in Roman London alone (Price 1998, pp. 337-38) including 70 kg from a pit in Basinghall, London (Shepherd, Wardle 2009) (fig. 1). Other assemblages of cullet appear to be from the point of collection, such as the basket of fragmentary glass found in a villa at Pisanella, Italy (Keller 2005) or the 8th/9th-century AD collection in Tower 1 at Butrint, Albania (Jennings, Stark 2012). There is also some evidence to show how cullet was transported to workshops, for example the barrel of broken glass discovered on *Iulia Felix*, a ship wrecked off the coast of northern Italy (Silvestri *et al.* 2008). These collections of glass can be identified as cullet because they include fragments from vessel forms spanning several centuries, and no complete objects.

Whilst most of the evidence described above relates to transparent glass (both naturally-coloured blue-green or colourless), opaque coloured glass was also sought after for recycling. Coloured glass was sometimes re-melted and re-used directly, or diluted by mixing it into a glass batch to make a larger volume but with a weaker colour. Coloured glass was sought particularly for making *tesserae* and increasingly for windows for churches and monastic buildings. Analytical evidence, discussed later,

suggests that much of this coloured glass was made using recycled Roman coloured glass, but there is also archaeological evidence to support this, notably from the site of the 9th-century monastery of San Vincenzo, Italy. Here glassworkers made vessels, windows, imitation gemstones and enamels in a wide range of hues. Glass mosaic tesserae were found, which glassworkers were adding to the glass melts for colour (Dell'Acqua 1997; Schibille, Freestone 2013). Some of the crucibles with remnants of glass contained occasional stone tesserae that had been added to the melt by mistake with the glass ones. Similar evidence has been found at Müstair in Switzerland (Kessler *et al.* 2013) and is corroborated by analyses of glass from numerous sites (Mirti *et al.* 2000; Foy *et al.* 2003; Wolf *et al.* 2005).

The previous examples all involve glass being melted down during the recycling process but sometimes glass objects were recycled without being re-melted. These are most easily identifiable as recycled if they are of a particular style or have decorative elements which link them specifically to a particular location or period. Items such as the mask medallions from Roman jugs and the decorated bases of late 4th-century bowls with images in gold leaf (Price, Cottam 1998; Howells 2013) were often reused. They were trimmed to function as keepsakes, lids and counters. Similarly broken coloured vessels were sometimes cut up to make mosaic tesserae (Paynter *et al.* 2015).

3.2. Documentary evidence

Recycling within the Roman world was so common that it was documented by a number of Roman authors. Roman poets, writing in the 1st century AD, such as Strabo and Martial, describe street peddlers collecting broken glass in exchange for sulphur, which was used for matches (Stern 1999, p. 450; Keller 2005).

The recycling of Roman glass continued in subsequent centuries, being used and re-melted by other societies and cultures. Perhaps the most famous description of this is Theophilus' treatise *De diversis artibus* in the 12th century AD (Dodwell 1986, pp. 44-45). Whereas the Roman recycling references probably apply mainly to transparent vessel and window glass, Theophilus specifically mentions opaque coloured glass tesserae, 'little square stones' in white, black, green, yellow, blue, red, and purple that were taken from the mosaics of ancient buildings, and small vessels of coloured glass. He emphasises that French glassworkers used the blue for windows, having sometimes diluted it with fresh colourless glass, and used purple and green in a similar way.

3.3. Analytical evidence

Chemical analysis, in combination with typological study and sound contextual information, can strongly indicate the use of recycled glass. In some instances the case for recycling is clear cut, such as when the glass used to make an object is a type that was no longer made by then, *i.e.* the glass is far older than the object itself. The examples given later in this paper both relate to the re-use of coloured Roman glass in the early 2nd millennium AD, both for window glass (Cox, Gillies 1986) and for vessels (Phelps 2011). More typically recycling is identified because the mixing or re-melting of cullet has resulted in changes to the glass composition (Jackson 1996; Jackson, Paynter 2015). These can be major changes, through the mixing or amalgamation of different raw glass compositions, or more subtle, with the accidental incorporation of tiny amounts of coloured glass containing added colouring minerals, or minor contamination from the furnace materials, glassworking tools or fuel.

Mixed glass compositions result when at least two different types of glass were recycled together and the end product is a hybrid composition somewhere in between. Sometimes the glass types that have been mixed were so clearly different visually that they must have been combined intentionally, for example when strongly coloured Roman tesserae were used to colour glass batches for making windows in the later 1st and early 2nd millennia AD (Cox, Gillies 1986; Wolf *et al.* 2005), confirming the descriptions by Theophilus. In other instances hybrids may have been created by accident because the glass types were visually similar and so were not properly separated when the cullet was sorted before re-use. This may have been the case in the Roman period because analysis has shown that a large proportion of the naturally-coloured blue-green glass in circulation is actually a recycled mixture of two originally colourless types; one type decolourised with manganese and the other with antimony. These colourless glass types were superficially similar and so more likely to be mixed together inadvertently (Jackson, Paynter 2015). Perhaps unexpectedly, the resulting recycled glass was sometimes colourless but sometimes blue-green depending on the proportions of each component. This demonstrates that the glassmaker might have more difficulty controlling the colour of the glass with recycled material as different elements would behave unpredictably when in combination. Particular care must be taken when recycling colourless glass if it is to remain colourless.

These hybrid compositions have formed the basis for many of the discussions of recycling in the literature (for example Jackson 1996, 2005a; Foster, Jackson 2010; Jackson, Paynter 2015; Freestone



Fig. 3. Fragments of broken glass vessels and waste surrounding a wood-fuelled crucible furnace used for experimental glassworking by Mark Hill and David Taylor. Much of this material would have been recycled, perhaps introducing contamination (see fig. 4).

2015). The real difficulty though is identifying recycling when the cullet *has* been carefully sorted into different compositional types and so 'like' is mixed with 'like', or in those periods or regions when one type of glass dominates the market and so the mixing of very small amounts of other primary groups is almost masked. How do we spot recycling then? In some instances it may not be possible to detect it. However, this is where the concept of 'contamination' becomes more important, because even with careful sorting eventually some coloured opaque glass would find its way into batches of transparent glass, perhaps by including fragments with coloured trails *etc.* Over time, this leads to slightly increased amounts of elements such as copper, lead and antimony in the glass compared to its starting composition (Jackson 1996, Ubaldi, Veritá 2003; Jackson 2005a; Freestone, Hughes 2006; Grünewald, Hartmann 2015). Therefore when colourants are present in colourless or naturally-coloured glass compositions, that originally would not have had any colourants added, it implies that recycling has allowed a small amount of coloured glass to find its way into the batch.

Accidental contamination also arises from the fumes or ash from the fuel used to heat the furnace, the walls of the furnace tank or crucible in which the glass was heated, or scale from the iron blowing iron used to shape the glass (Paynter 2008) (figs. 3, 4). The level of contamination is unpredictable but is likely to increase with the number of rounds of recycling, and if high temperatures are used for long periods. In modern gas-fired furnaces some of the alkali (notably sodium oxide) is lost from the glass as a gas during prolonged or repeated heating, which can affect the working properties of the glass, but this is not the case in the



Fig. 4. Iron oxide scale from a blowing iron dissolving in a Roman-type glass during an experimental glassworking project by Mark Hill and David Taylor; the affected glass turns green demonstrating how contamination can alter the glass colour.

furnaces used in antiquity. These furnaces used wood fuel instead, which released another alkali gas, potassium oxide, on burning so the alkali content may have actually increased (Paynter 2008). Particles of wood ash may also be absorbed by the glass leading to increases in calcium, magnesium and phosphorus oxides. Although tank furnaces were used to produce primary glasses, both tank and crucible furnaces were used for re-melting. The extent of the contamination from the crucible or furnace materials depended on the composition of both, the surface area to volume ratio (particularly high for small crucibles), as well as time and temperature, and could lead to increased concentrations of iron and aluminium oxides in the glass (Jackson, Paynter 2015). Therefore if the levels of potassium, phosphorus and iron oxides, and to a lesser extent aluminium oxide, are elevated in a glass it can also indicate contamination during recycling. Eventually special clays, more resistant to high temperatures and chemical attack, were used to make glass crucibles but this was not until later in the medieval period (Paynter 2009).

4. Key changes in glass composition in the 1st millennium AD

Recognising recycling in glass is about being able to identify elements that should not be present, *i.e.* they are not found in the glass originally,

when it is first made, and are unlikely to have been added intentionally since. So it is important to first establish the compositions of the main types of newly-made glass in circulation in a particular time and place. The successful identification of these 'production groups' for Roman glasses has provided a basis for our understanding of the primary compositions in circulation at any one period and show that there are two key technological changes in the 1st millennium AD. One of these is related to the additives used both to decolorise and colour the glass and the second is a fundamental change in the raw materials used to form the glass. Recognising these changes, and when they take place, allows us to better identify recycled material in the archaeological record.

The first change concerns antimony, which was an important component of high status colourless glass and also opaque coloured glass in the Roman period. The replacement of antimony with alternatives from around the mid-4th century AD suggests that the mineral containing antimony either was unavailable to the glassmakers or became scarce around this time. The second development is that plant ash glass begins to increasingly replace natron glass types, particularly from the 9th century AD. These important changes which influence glass compositions can be used to explore recycling in glasses using an analytical approach, and are described in more detail below.

4.1. Decolourisers and opacifiers: the importance of antimony

A key development in the 1st millennium AD was the widespread distribution of glass with added antimony oxide, thought to originate in Egypt (Sayre 1963; Jackson, Paynter 2015). Antimony oxide was very effective at neutralising the natural colour of glass (when dissolved in it), resulting in a colourless glass that was used fairly exclusively for high status tablewares (see fig. 2). Sometime in the mid-4th century AD however, this antimony decolorised glass essentially disappears, not just in Europe but in the Eastern Mediterranean as well (see fig. 5). It is replaced to some extent by glasses decolorised by manganese, another element used widely as a decoloriser although slightly less effective in this role. Antimony compounds could also be used as additives to make glass opaque (fig. 2). In this case the antimony is not dissolved in the glass, it is combined with other substances to make tiny crystals that scattered light. Although antimony opacifiers are found in glass objects from the 2nd millennium BC onwards in the Near East and Egypt (Lilyquist, Brill 1993; Jackson 2005b), they only become widespread across Europe in the Late Iron Age and Roman period, particularly the 1st and 2nd centuries AD. By the 5th century AD however, alternatives were being

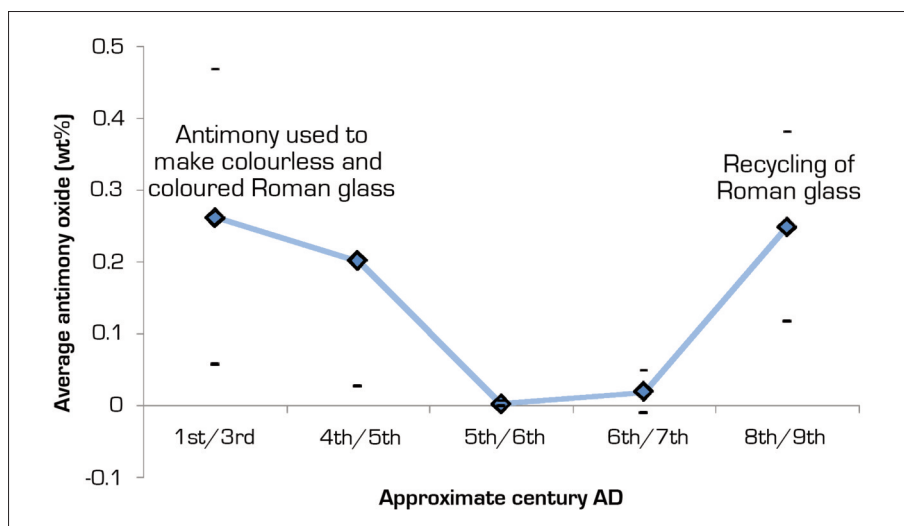


Fig. 5. The average concentrations of antimony oxide observed in assemblages of colourless and naturally-coloured glasses by broad date, from the 1st to 9th century AD. The increasing antimony content in the 7th/8th centuries is due to the recycling of Roman glass. Data taken from Jackson and Paynter 2015 (193 samples, 1st-3rd), Foster and Jackson 2009, 2010 (644 samples, 4th/5th), Hunter and Heyworth 1998 (230 samples, 8th/9th), all assemblages from the UK, plus Foy *et al.* 2003 (16 and 22 samples respectively, 5th/6th and 6th/7th), all assemblages from France. The bars show 1 standard deviation either side of each datapoint. The average is influenced by the proportion of colourless to naturally-coloured glass in the assemblages, and so representative mixed assemblages have been used. Although a smaller sample, the 5th/7th-century assemblages are nonetheless representative (e.g. Cholakova *et al.* 2015).

sought and there was a switch to tin-based opacifiers in some regions (Rooksby 1962, 1964; Paynter *et al.* 2014). Elsewhere glassworkers resorted to adding quartz (Arletti *et al.* 2010) or crushed bone to their glass to make it more opaque (Marii, Rehren 2009; Silvestri *et al.* 2016). These technological adaptations imply a shortage of antimony to make colourants and opacifiers for coloured glass as well.

Thus, the mid-4th century AD is a pivotal time in glass production because antimony appears to become scarce. It is no longer used to make fresh antimony-decolourised glass on any significant scale and producers of coloured opaque glass start using alternatives to antimony, such as tin oxide, bone or quartz, or recycling old coloured glass. When small concentrations of antimony are found in glass post-dating the 4th century AD there is therefore a strong possibility that it contains recycled Roman glass (Jackson 2005a).

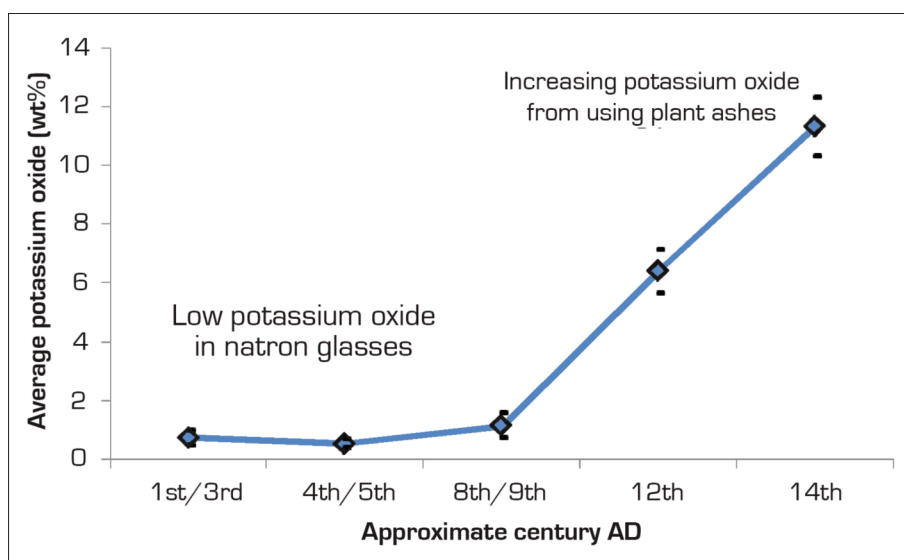


Fig. 6. The average concentrations of potassium oxide observed in UK assemblages of colourless, naturally-coloured and blue coloured glasses by broad date, from the 1st to 14th centuries AD. The rising potassium content after the 9th century is due to the increased recycling and the use of plant ashes to make glass. Data for natron glasses are taken from Jackson and Paynter 2015 (193 samples, 1st-3rd), Paynter *et al.* 2015 (19 samples, 1st-3rd), Foster and Jackson 2009, 2010 (644 samples, 4th/5th) and Hunter and Heyworth 1998 (230 samples, 8th/9th). These are compared to window glass from Glastonbury, which are plant ash glass mixed with older natron glass (3 samples, approximately 12th century: Caple, Barnett 2012), and 14th-century glasses made from plant ashes in Staffordshire (28 samples, Meek *et al.* 2012 and author's unpublished data). The bars show 1 standard deviation either side of each datapoint.

4.2. Fluxes: natron and plant ashes

Glasses produced with the naturally occurring evaporite, natron, have a distinct chemical composition, with relatively low concentrations (generally below 1.5wt%) of potassium oxide and magnesium oxide. In contrast glasses made with plant ash fluxes vary considerably in their composition, depending on the type of plant, where it grew, when it was harvested and how the ash was prepared. Plant ash glass was produced before and after the Roman period in the western world, but the generic types of plant ashes differed between the two periods. Early plant ash glasses, such as those made in Egypt and the Near East in the 2nd/1st millennium BC, were made with the ashes of salt-tolerant plants. These glasses were high in sodium oxide, very like natron glass-

es, but their compositions differ in the concentrations of potassium oxide and magnesium oxide which are generally between 1.5wt% and 5wt%. Glasses produced in Western Europe from around the 10th century AD and later used wood ashes derived from hardwoods and forest plants. These glasses are distinctive as they usually contain less sodium (below 10wt%) but more potassium oxide (up to 20wt%) and magnesium oxide (above 5wt%) (fig. 6). Glasses made with plant ashes often contain increased levels of phosphorous oxide as well.

Therefore the concentrations of potassium, magnesium and phosphorus oxides in a glass can be used as an indicator of the use of plant ashes. This characteristic can be useful for identifying recycling because towards the end of the 1st millennium AD, and beginning of the 2nd, as natron glass production declined and plant ash glass production spread, glasses often have characteristics of both natron and plant ash (Smith 1963; Gratuze, Barrandon 1990; Henderson *et al.* 2004). There is an increase in potassium, magnesium and /or phosphorus, but not to the levels observed in glasses produced with plant ash as the sole flux. The transition between natron and plant ash glasses has been charted for tesserae and coloured window glass, but where examples have characteristics of both it can be difficult to determine whether the plant ashes were added deliberately or accidentally through contamination (Freestone *et al.* 1990; Ubaldi ,Verità 2003; Arletti *et al.* 2010; Caple, Barnett 2012). It is also important to bear in mind that plant ash glasses were used continuously throughout the Roman period in some parts of the Near East, rather than the more typical natron glasses, and that plant ashes were added to some coloured Roman glass as part of the colourant, particularly red, green and black (Paynter *et al.* 2015; Jackson, Cottam 2015) (only opaque blue coloured glasses have been included in fig. 6).

5. Discussion

5.1. Chronological variations in recycling

There was a significant reduction in the amount of glass being used in the western regions from the mid-4th century AD onwards (Tyson 2000) but it is evident that new glass was still being produced, because furnaces dating to this period have been excavated in the Syria-Palestine region of the Eastern Mediterranean. In regions near to furnace sites (for example at Dor, Appolonia and Jalame, and at Bet Eliezer) the glass

made in those furnaces dominates nearby assemblages (Greiff, Hartmann 2013; Nenna 2015) but it makes up only a minor proportion of the material from Western Europe from the mid-4th to the 7th or 8th centuries AD (Foy *et al.* 2003), and so the supply of new glass outside the immediate contact zone was more sporadic.

Analytical studies of glass from the Roman, antique and early medieval periods in Europe show successive waves of new glass, each with a slightly different composition and a lifespan varying from decades to centuries. Each of these compositions has a relatively broad distribution in Western Europe and further afield (Foy *et al.* 2003; Foster, Jackson 2009, 2010; Cholakova *et al.* 2015; Ceglia *et al.* 2015; Maltoni *et al.* 2015). This is an indication that glass was still being made on a large scale and widely distributed but that there were a number of changes over time in the raw materials used, and perhaps where the glass was being made and by whom. These changes suggest that the supply to Western Europe during this later Roman and early antique period is biased towards production centres as yet unidentified, rather than those known in Syria-Palestine. The olive green glass that dominates in the later 4th/5th centuries AD is thought to originate in Egypt (Foster, Jackson 2009), and this is followed by other distinctive compositions in the 5th/6th centuries AD (Foy *et al.* 2003; Cholakova *et al.* 2015) and another in the 6th/8th centuries AD (Foy *et al.* 2003; Freestone *et al.* 2008; Ceglia *et al.* 2015). These supplies are interrupted at intervals however, and it is in these transitional periods that evidence for more intensive recycling of transparent glass has been identified. For example Grünewald and Hartmann (2015) used analyses of closely dated glass vessels from burial contexts to argue that recycling increased in certain periods, particularly from AD 260 to 370, and from about AD 430 to 500. This interpretation was based on elevated levels of lead, antimony and copper in the glass from these date ranges.

With each wave of fresh glass, both new and old compositions would be in circulation for a while and might be recycled together, particularly if they appeared visually similar. An example is provided by Foster and Jackson (2009), who studied glass from the mid-4th/5th centuries AD from sites in Britain and identified two naturally-coloured glass types; one with a stronger olive green to brown hue and the other a paler colour. A major proportion of the paler glass analysed contained minor amounts of antimony. This contamination suggested that the more weakly coloured of the new glasses was being recycled with the outgoing old Roman glass, which was by then becoming increasingly rare (fig. 7).

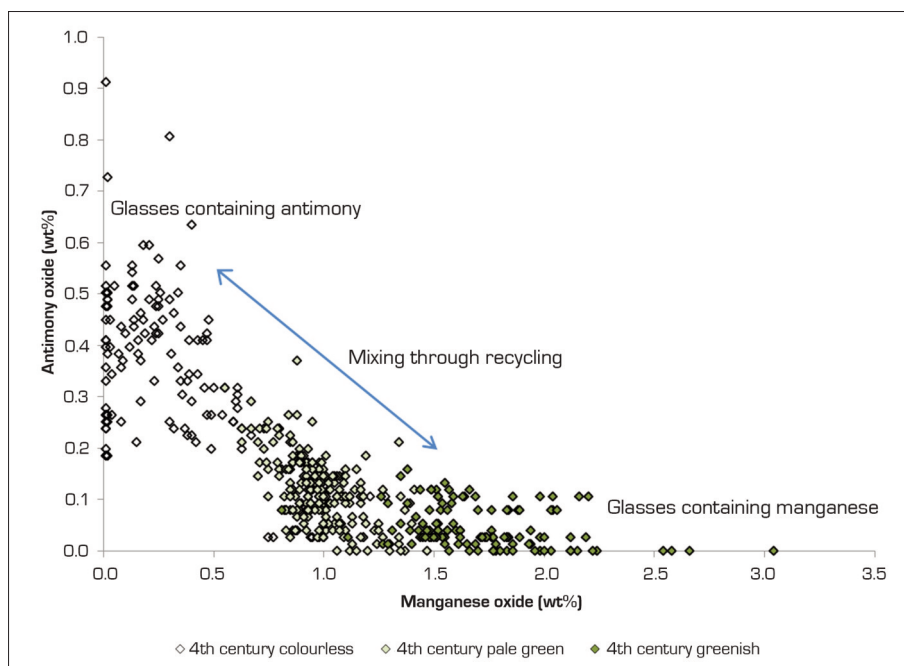


Fig. 7. The chart shows the concentrations of antimony oxide and manganese oxide in 4th-century colourless, pale green and darker green glass from the UK (Foster, Jackson 2009, 2010). When made, each type of glass would have contained either antimony or manganese: as a result of recycling however, many now contain both.

The widespread re-introduction of plant ash glass from around the 9th century AD would eventually lead to numerous alternative sources of transparent glass for glassworkers in Europe, and a change in how the glass industry was organised, with glass often being made and worked at the same site. However the production of *coloured* glass was also dependent on sources of particular metal minerals, and the knowledge of how to use them to make colourants and opacifiers. It appears that these materials or skills were in short supply because demand for brightly coloured glass was often met by recycling coloured Roman glass, and this continued through the remainder of the 1st millennium AD and into the early 2nd millennium AD. The presence of antimony opacifiers or low levels of colourants in the 5th/6th-century windows from Sion and the 7th-century window glass used at Jarrow in England (Freestone, Hughes 2006) suggest that the glass contained a proportion of recycled Roman material. By the 8th century in Hamwic, England, glass with similar levels

of contamination was used for vessels (Hunter, Sanderson 1998). In fact the recycling of Roman glass continued into the 12th century, 700 hundred years after it was first made, even though fresh plant ash glass was now available. For specialist, high status vessels it seems that coloured Roman glass was sometimes re-used undiluted (Gratuze *et al.* 1997; Phelps 2011), but more often it was mixed with plant ash glass to produce larger volumes and more dilute colours (Cox, Gillies 1986; Caple, Barnett 2012; Kunicki-Goldfinger *et al.* 2014).

5.2. Regional variations in recycling

The previous examples illustrate that glass recycling was common and widespread, but interestingly much of the analytical data to indicate recycling has come from studies in Western Europe (for example Sayre, Smith 1961; Foy *et al.* 2003; Wolf *et al.* 2005; Foster, Jackson 2009; Schibille, Freestone 2013; Jackson, Paynter 2015; Grünewald, Hartmann 2015). In contrast, the furnaces producing new glass during this period have so far been found in the Eastern Mediterranean (Nenna 2015) near the sources of natron and suitable sand necessary to make the glass. The distant workshops and consumers using glass in Western Europe were therefore dependent on trade networks extending from the Eastern Mediterranean and across Europe (Grünewald, Hartmann 2015). These sites, at some distance from the main production centres, tend to be supplied by glass from more than one source whereas a single glass type often dominates at sites near to a particular production centre (Greiff, Hartmann 2013). They would also have been further along in the supply chain and so would have been more likely to be melting cullet in addition to raw glass supplied directly from the production centres. Recycling is easier to detect through analysis in these areas because of the diverse range of glass compositions in use; with analysis it is far easier to identify recycling when dissimilar glasses are mixed than when like is mixed with like. Archaeological sites remote from production centres therefore provide an ideal opportunity to study and detect recycling but recycling in other areas should not be discounted, it may simply be more difficult to detect.

5.3. The organisation of recycling

Recycling is often discussed in general terms, but the evidence drawn together in this paper reveals vast differences in scale, motivation and practice, varying between routine or specialised and potentially large-



Fig. 8. Partially melted Roman windows amongst a cullet dump from Basinghall, London (courtesy of MOLLA). The adhering material would result in contamination of the glass.

scale recycling followed by redistribution. There is ample evidence that glassworkers routinely collected and used cullet for recycling, this was the case even when glass was in relatively plentiful supply as in Roman London (fig. 1, fig. 8). For some specialised applications glassworkers recycled particular types of glass where they were unable to otherwise achieve the effect that they wanted. This was particularly important for the production of coloured glass, which led to Roman coloured glass being sought and selectively recycled as late as the 12th century AD. Finally some glass workshops may have recycled on a larger scale and redistributed the recycled glass widely. There is tentative evidence for this from the Roman period, for example analysis suggests that a cake of turquoise coloured Roman glass found in southern Britain was made by adding colourants to recycled glass (Paynter *et al.* 2015). The coloured glass was then formed into a cake and traded on before being used to make tesserae (shown in fig. 2). Similarly much of the naturally-coloured Roman glass found in Britain is recycled, made from a mixture of antimony and manganese decolourised glasses, as mentioned previously (Jackson, Paynter 2015). However manganese decolourised glass appears to be fairly rare in Britain during this period. This raises the possibility that most of this hybrid glass was mixed before reaching Britain, at the end

of a long supply chain. The recycled hybrid mixture was often used for bottles and windows (fig. 8), which required large volumes of naturally-coloured glass and so glassworkers may have recycled glass on a larger scale to make these products, and could be less discriminating in the range of cullet that they used. In Britain, glassworkers recycled these objects once again, at glassworking sites like Leicester and Mancetter where these hybrid compositions are seen in cullet and in melted waste (Jackson *et al.* 1991).

6. Conclusions

Scientific analysis has helped archaeologists to better understand the complex lifecycle of glass in the past. Large analytical programmes studying glass compositions during different periods and across wide regions, in combination with thorough archaeological recording and expert typological study, have demonstrated that the recycling of glass was prolific. Antimony, in particular, has proved to be a very useful element for detecting the recycling of Roman glass but this element is difficult to detect in small quantities with some instrumentation and so unfortunately is not always included in published studies.

Contemporary or consecutive glass types were most often recycled together, but there are exceptions where ancient glass has been reused many centuries later. There is no time limit on recycling natron glass because it tends not to spoil over time; once made it joins the reservoir available for recycling for centuries to come. As the picture of recycling grows through scientific analysis and archaeological discovery, patterns in the archaeological record will become apparent and it will be possible to enhance this exploration as to why recycling was more prevalent in particular times and places or for certain applications, and how glassworkers sorted and reworked glass during recycling. We have demonstrated here that the extent, scale and purpose of recycling differ chronologically, regionally and by application. Whilst the availability of fresh glass appears to have been an important factor when considering larger scale recycling and the redistribution of recycled glass, recycling was also undertaken routinely at workshops and selectively for specialised applications, particularly where there was demand for certain glass colours after the 4th century AD. The examples given here show that 'recycling' encompasses many different practices, varying greatly in scale and significance, and undertaken for a range of reasons, which analytical studies now have the potential to reveal.

Regions far removed from the furnace sites making the fresh glass, such as Western Europe, make useful case studies. They were dependent on long distance trade routes and were supplied with glass from multiple or varying sources, which tends to make recycling both common and easier to detect, because mixtures of dissimilar glasses are easier to identify. But there are other more subtle indicators of recycling too, such as the contamination from furnace and crucible materials, tools and fuel, which may point to the likelihood of recycling. By using chemical analysis to actively look for recycled glass in collections of cullet, in traded chunks or cakes of glass, in waste from glass workshops and in finished items, we are able to build a far clearer picture of the lifecycle of glass in the past; a cycle that sometimes lasted a thousand years.

References

- R. ARLETTI, C. FIORI, M. VANDINI 2010, *A study of glass tesserae from mosaics in the monasteries of Daphni and Hosios Loukas (Greece)*, "Archaeometry", 52 (5), pp. 796-815.
- R.H. BRILL 1988, *Scientific investigations of the Jalame glass and related finds*, in G.D. WEINBERG (ed), *Excavations at Jalame: Site of a Glass Factory in Late Roman Palestine*, Columbia, pp. 257-294.
- R.H. BRILL 1999, *Chemical Analysis of Early Glasses*, New York.
- C. CAPLE, R. BARNETT 2012, *Glastonbury Abbey Durable Blue Medieval Window Glass in, Glastonbury Abbey: Archaeological Excavations 1904 – 1979*, Unpublished report from Archaeology Data Service.
- A. CEGLIA, P. COSYNS, K. NYS, H. TERRY, H. THIENPONT, W. MEULEBROECK 2015, *Late antique glass distribution and consumption in Cyprus: a chemical study*, "Journal of Archaeological Science", 61, pp. 213-222.
- A. CHOLAKOVA, T. REHREN, I.C. FREESTONE 2015, *Compositional identification of 6th c. AD glass from the Lower Danube*, "Journal of Archaeological Science: Reports", doi: 10.1016/j.jasrep.2015.08.009.
- G.A. COX, K.J.S. GILLIES 1986, *The X-ray fluorescence analysis of medieval durable blue soda glass from York Minster*, "Archaeometry", 28(1), pp. 57-68.
- F. DELL'ACQUA 1997, *Ninth-century window glass from the Monastery of San Vincenzo al Volturno (Molise, Italy)*, "Journal of Glass Studies", 39, pp. 33-41.
- C.R. DODWELL 1986, *Theophilus. The Various Arts (De diversis artibus), Book II, XII, "The Various Colours of Opaque Glass"*, Oxford, pp. 44-45.
- H. FOSTER, C.M. JACKSON 2009, *The composition of 'naturally coloured' late Roman vessel glass from Britain and the implications for models of glass production and supply*, "Journal of Archaeological Science", 36, pp. 189-204.
- H. FOSTER, C.M. JACKSON 2010, *The composition of late Romano-British colourless vessel glass: glass production and consumption*, "Journal of Archaeological Science", 37(12), pp. 3068-3080.
- D. FOY, M. PICON, M. VICHY, V. THIRION-MERLE 2003, *Caractérisation des verres de la fin de l'Antiquité en Méditerranée occidentale: l'émergence de nouveaux courants commerciaux*, in D. FOY, M.-D. NENNA (eds), *Échanges et commerce du verre dans le monde antique*, Montagnac, pp. 41-85.
- D. FOY, M. VICHY, M. PICON 2000, *Lingots de verre en Méditerranée occidentale*, in *Annales du 14^{ème} Congrès de l'Association Internationale pour l'Histoire du Verre*, Amsterdam, pp. 51-57.
- I.C. FREESTONE 2006, *Glass production in Late Antiquity and the early Islamic period: a geochemical perspective*, in M. MAGGETTI, B. MESSIGA (eds), *Geomaterials in Cultural Heritage*, London, pp. 201-216.
- I.C. FREESTONE, M. BIMSON, D. BUCKTON 1990, *Compositional categories of Byzantine glass tesserae*, in *Annales du 11^e Congrès de l'Association internationale pour l'histoire du verre (Bâle, 1988)*, Amsterdam, pp. 271-280.
- I.C. FREESTONE, M.J. HUGHES 2006, *Origins of the Jarrow glass*, in R. CRAMP, *Wearmouth and Jarrow Monastic Sites Volume 2*, London, pp. 147-155.
- I.C. FREESTONE, M.J. HUGHES, C.P. STAPLETON, 2008, *The Composition and Production of Anglo-Saxon Glass*, in V.I. EVISON, *Catalogue of Anglo-Saxon Glass in the British Museum*, London, pp. 29-46.
- B. GRATUZE, J.N. BARRANDON 1990, *Islamic glass weights and stamps - analysis using nuclear techniques*, "Archaeometry", 32, pp. 155-162.
- B. GRATUZE, I. SOULIER, J.N. BARRANDON 1997, *L'analyse chimique, un outil au service de l'histoire du verre*, "Verre", 1, pp. 9-20.
- S. GREIFF, S. HARTMANN 2013, *"Wer kriegt was?": Untersuchungen zur Verbreitung spätantiker und frühmittelalterlicher Glasgruppen in Europa und dem Mediterraneum anhand von Fallbeispielen*, "Archäometrie und Denkmalpflege", pp. 251-255.
- M. GRÜNEWALD, S. HARTMANN 2015, *Überlegungen zum Glasrecycling der Antike im Bereich des heutigen Deutschlands*, in P. HENRICH, CH. MIKS, J. OBMANN, M. WIELAND (eds), *Non solum sed etiam. Festschrift für Thomas Fischer zum 65. Geburtstag*, Rahden, pp. 153-164.

- J. HENDERSON, S.D. McLOUGHLIN, D.S. MCPHAIL 2004, *Radical changes in Islamic glass technology: evidence for conservatism and experimentation with new glass recipes from early and middle Islamic Raqqa, Syria*, "Archaeometry", 46, pp. 439-468.
- D. HOWELLS 2013, *Making Late Antique gold glass*, in C. ENTWISTLE, E. JAMES (eds), *New Light on Old glass; Recent research on Byzantine mosaics and glass*, London, pp. 112-120.
- J.R. HUNTER, M.P. HEYWORTH 1998, *The Hamwic Glass*, York.
- C.M. JACKSON 1996, *From Roman to early medieval glasses. Many happy returns or a new birth?*, in *Annales du 13^e Congrès de l'Association Internationale pour l'Histoire du Verre* (Pays Bas, 1995), Lochem, pp. 289-301.
- C.M. JACKSON 2005a, *Making colourless glass in the Roman period*, "Archaeometry", 47(4), pp. 763-780.
- C.M. JACKSON 2005b, *Glassmaking in Bronze Age Egypt*, "Science", 308, pp. 1750-1752.
- C.M. JACKSON, S. COTTAM 2015, *'A green thought in a green shade'; compositional and typological observations concerning the production of emerald green glass vessels in the 1st century AD*, "Journal of Archaeological Science", 61, pp. 139-148.
- C.M. JACKSON, J.R. HUNTER, S.E. WARREN, H.E.M. COOL 1991, *The analysis of blue-green glass and glassy waste from two Romano-British glass working sites*, in E. PERNICKA, G.A. WAGNER (eds) *Archaeometry '90. International Symposium on Archaeometry* (Heidelberg, 2-6 April 1990), Basel, pp. 295-305.
- C.M. JACKSON, S. PAYNTER 2015, *A great big melting pot. Patterns of glass supply, consumption and recycling in Roman Coppergate, York*, "Archaeometry". Doi: 10.1111/arcim.12158.
- C.M. JACKSON, S. PAYNTER, M.-D. NENNA, P. DEGRYSE in preparation, *Soda from el-Barnuqi (al-Barnuq), Egypt, and its potential use for Roman glass manufacture*.
- S. JENNINGS, STARK 2012, *Appendix: the glass from Tower 1 in the Western Defences*, in I.L. HANSEN, R. HODGES, S. LEPPARD (eds), *Butrint 4. The Archaeology and Histories of an Ionian Town*, Oxford, pp. 257-259.
- D. KELLER 2005, *Social and economic aspects of glass recycling*, J. BRUHN, B. CROXFORD, D. GRIGOROPOULOS (eds), *TRAC 2004, Proceedings of the Fourteenth Annual Theoretical Roman Archaeology Conference*, Oxford, pp. 65-78.
- C.M. KESSLER, S. WOLF, S. TRÜMPLE 2013, *Leuchtende Fenster: Glas als Werkstoff und seine Herstellung*, in M. RIEK, J. GOLL, G. DESCŒUDRES (eds), *Die Zeit Karls des Grossen in der Schweiz*, Bern, pp. 224-227.
- J. KUNICKI-GOLDFINGER, I.C. FREESTONE, I. McDONALD, J.A. HOBOT, H. GILDERDALE-SCOTT, T. AYERS 2014, *Technology, production and chronology of red window glass in the medieval period – rediscovery of a lost technology*, "Journal of Archaeological Science", 41, pp. 89-105.
- C. LILYQUIST, R.H. BRILL 1993, *Studies in Early Egyptian glass*, New York.
- S. MALTONI, T. CHINNI, M. VANDINI, E. CIRELLI, A. SILVESTRI, G. MOLIN 2015, *Archaeological and archaeometric study of the glass findings from the ancient harbour of Classe (Ravenna- Italy): new evidence*, "Heritage Science", 3(13), DOI: 10.1186/s40494-015-0034-5
- F. MARII, TH. REHREN 2009, *Archaeological coloured glass cakes and tesserae from the Petra Church*, in, *Annales of the 17th Congress of the AIHV* (Antwerp, 2009), Amsterdam, pp. 295-300.
- F.R. MATSON, G. RINDONE (eds) 1963, *Advances in Glass Technology, Part 2*, New York.
- A. MEEK, J. HENDERSON, J. EVANS 2012, *Isotope analysis of English forest glass from the Weald and Staffordshire*, "Journal of Analytical Atomic Spectrometry", 27, pp. 786-795.
- P. MIRTÌ, A. LEPORA, L. SAGUI 2000, *Scientific analysis of seventh-century glass fragments from the Crypta Balbi in Rome*, "Archaeometry", 42, pp. 359-374.
- M.-D. NENNA 2015, *Primary glass workshops in Graeco-Roman Egypt: preliminary report on the excavations of the site of Beni Salama, Wadi Natrun (2003, 2005-9)*, in J. BAYLEY, I.C. FREESTONE, C.M. JACKSON (eds), *Glass of the Roman World*, Oxford, pp. 1-22.

- S. PAYNTER 2008, *Experiments in the reconstruction of Roman wood-fired glassworking furnaces: waste products and their formation processes*, "Journal of Glass Studies", 50, pp. 271-90.
- S. PAYNTER 2009, *The importance of pots: the role of refractories in the development of the English glass industry during the 16th/17th centuries*, in D. IGNATIADOU, A. ANTONARAS (eds), *Annales du 18^e congrès de l'association internationale pour l'histoire du verre*, Thessaloniki, pp. 419-424.
- S. PAYNTER, T. KEARNS, H. COOL, S. CHENERY 2015, *Roman coloured glass in the Western provinces: the glass cakes and tesserae from West Clacton in England*, "Journal of Archaeological Science", 62, pp. 66-81.
- S. PAYNTER, J. PRICE, S. JENNINGS 2014, *Glass-working at Whitby Abbey and Kirkdale Minster in North Yorkshire*, in D. KELLER, J. PRICE, C.M. JACKSON (eds), *Neighbours and Successors of Rome: Traditions of Glass Production and use in Europe and the Middle East in the Later 1st Millennium AD*, Oxford, pp. 32-42.
- M. PHELPS 2011, *35-39 South Main Street, Cork, Ireland. Analysis of medieval glass vessels*, English Heritage Research Department Report 9-2011.
- J. PRICE 1998, *The social context of glass production in Roman Britain*, in P. McCRAY (ed), *The Prehistory and History of Glass-making Technology*, Westerville (Ohio), pp. 331-348.
- J. PRICE, S. COTTAM 1998, *Romano-British glass vessels: a handbook*, York.
- H.P. ROOKSBY 1962, *Opacifiers in opal glasses through the ages*, "G.E.C. Journal", f2(1), pp. 20-26.
- H.P. ROOKSBY 1964, *A yellow cubic lead tin oxide opacifier in ancient glasses*, "Physics and Chemistry of Glasses", 2(1), pp. 20-25.
- E.V. SAYRE 1963, *The intentional use of antimony and manganese in ancient glasses*, in MATSON, RINDONE 1963, pp. 263-282.
- E.V. SAYRE, R.W. SMITH 1961, *Compositional categories of Ancient Glass*, "Science", 133, pp. 1824-1826.
- N. SCHIBILLE, I.C. FREESTONE 2013, *Composition, production and procurement of glass at San Vincenzo al Volturno: an early medieval monastic complex in Southern Italy*, "Plos one", Doi: 10.1371/journal.pone.0076479.
- J. SHEPHERD, A. WARDLE 2009, *The Glassmakers of Roman London*, London.
- A. SILVESTRI, G. MOLIN, G. SLAVIULO 2008, *The colourless glass of Iulia Felix*, "Journal of Archaeological Science", 35(2), pp. 331-341.
- A. SILVESTRI, F. NESTOLA, L. PERUZZO 2016, *Multi-methodological characterisation of calcium phosphate in late-Antique glass mosaic tesserae*, "Microchemical Journal", 124, pp. 811-818.
- R.W. SMITH 1963, *Archaeological evaluation of analyses of ancient glass*, in MATSON, RINDONE 1963, pp. 283-290.
- E.M. STERN 1999, *Roman glassblowing in a cultural context*, "American Journal of Archaeology", 103, pp. 441-484.
- W.E.S. TURNER 1956, *Studies of ancient glass and glassmaking processes. Part V: Raw materials and melting processes*, "Journal of the Society of Glass Technology", 40, pp. 276-299.
- R. TYSON 2000, *Medieval Glass Vessels Found in England c. AD 1200-1500*, York.
- M. UBOLDI, M. VERITÀ 2003, *Scientific analyses of glasses from late antique and early medieval archaeological sites in Northern Italy*, "Journal of Glass Studies", 45, pp. 115-137.
- S. WOLF, C.M. KESSLER, W.B. STERN, Y. GERBER 2005, *The composition and manufacture of early Medieval coloured window glass from Sion (Valais, Switzerland) – a Roman glass making tradition or innovative craftsmanship?*, "Archaeometry", 47, pp. 361-380.